

Performance of nano structured dye-sensitized solar cell utilizing natural sensitizer operated with platinum and carbon coated counter electrodes

M. Hossein. Bazargan

Advanced Materials and Renewable Energies Department
Iranian Research Organization for Science and Technology (IROST)
Forsat St. 71, Ferdoosi Sq., P. O. Box: 15815-3538, Tehran, Iran

Email: mbazargan@yahoo.com , Tel/Fax: +98(21)88826692

Abstract: Dye sensitized solar cell (DSSC) fabrication procedure has been employed using natural pomegranate juice for sensitization of nanocrystalline TiO_2 . Platinum and graphite coated electrodes were prepared by pulse current electrodeposition and soot staining method for use as counter electrodes. Photovoltaic parameters like short circuit current (I_{SC}), open circuit voltage (V_{OC}) and fill factor (FF) were evaluated for fabricated cells. Although the fill factor for both cells was found to be 45%, I_{SC} and V_{OC} for cells operating with carbon and platinum coated counter electrodes were increased from 360 to 400 mV and from 175 to 200 μA respectively. Overall conversion efficiencies of fabricated DSSC found to be 1.5 % for cell operated with platinum electrodeposited and 0.9 % for carbon coated counter electrodes.

Key words: Dye sensitized solar cell, photovoltaic performance, pomegranate juice, Platinum electrodeposition, carbon counter electrode.

1. Introduction

Dye-sensitized solar cells (DSSCs) [1] have attracted much attention for the last more than a decade. The DSSC consists of a dye-covered, nanoporous TiO_2 (titanium dioxide) layer and an electrolyte containing a redox mediator (I^-/I_3^-) encapsulated between two glass plates as shown in Fig. 1.

On the surface of the TiO_2 , a monolayer of dye molecules is adsorbed. The huge nanoporous surface allows for an adsorption of a sufficiently large number of dye molecules for efficient light harvesting. Front and counter substrates are coated with a transparent conducting oxide (TCO). Fluorine doped tin oxide (FTO) is most commonly used. The TCO glass at the counter electrode is coated with few atomic layers of

carbon or platinum, in order to catalyze the redox reaction with the electrolyte.

Electron kinetics in the nanocrystalline TiO_2 layer plays an important role in the operation of a dye solar cell. The electron injection from the excited dye to TiO_2 takes place in femtoseconds while the time scale for the back electron transfer is several orders of magnitude slower, indicating the charge separation achieved on kinetic grounds. The dye regeneration process occurs in nanoseconds scale explaining the efficient operation of the dye solar cell since the oxidized dye should be reduced to its ground state as fast as possible. The injected electrons to TiO_2 hop through the colloidal structure and finally arrive at the conducting glass collector [2], [3] and [4].

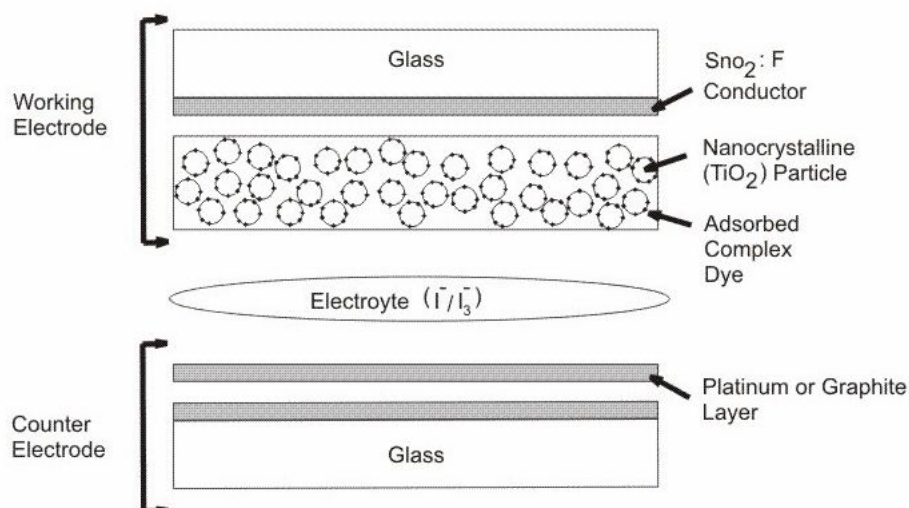


Fig.1 Schematic of a dye solar cell.

The adsorption of the dye to the nc-TiO₂ surface usually takes place via special anchoring groups attached to the dye molecule. The high efficiency of the dye sensitized solar cell is accomplished by coating the internal surfaces of the porous TiO₂ electrode with special dye molecules tuned to absorb the incoming photons [5] and [6].

Our aim was to investigate the performance of a sensitized solar cell with natural pomegranate juice operated with two different counter electrodes.

2. Experimental

2.1. Materials

Transparent conductive oxide coated glass (TCO 10-10, 2 cm × 2 cm) and Ti-Nanoxide D were purchased from Solaronix. Dinitroamine Platinum (II) were procured from Johnson Matthey Catalysts for platinum electrodeposition. Acetonitrile, sodium carbonate and sodium acetate (Aldrich) were used for electrolyte preparation.

2.2. Preparation

Ti-Nanoxide was deposited on TCO glass having resistance of 10 Ohm/cm² by tape casting technique and sintered in 450°C for 30 minutes. The working electrode (TiO₂ electrode) was immersed in freshly squeezed pomegranate juice for 12 hours. Pt counter electrode was prepared on TCO glass by pulse current electrodeposition method [7]. Electrodeposition was carried out using an aqueous solution of 16 ml of

Dinitroamine Platinum (II), 100 gr of sodium carbonate and 40 gr of sodium acetate in 1000 ml of distilled water. Pt electrode was prepared by current density of 0.2 A / dm² with the 10 s on-time and 10 s off time at room temperature. TCO glass, Pt wire and Ag/AgCl were used as the working, counter and reference electrodes respectively. Carbon coated counter electrode was prepared on TCO glass by soot staining method. The TCO glass was placed on top of a burning candle to apply a light carbon film to the entire conductive side of the plate. Electrolyte solution was prepared by taking the proportionate quantity of 0.5 mol KI and 0.05 mol of iodine in 20 ml acetonitrile solvent [8].

2.3. DSSC assembly

The immersed TiO₂ electrode in pomegranate juice was removed and rinsed with ethanol and was dried at 80°C for 10 minutes. The stained TiO₂ films and the Pt counter electrodes were assembled into sealed sandwich-type cells by heating with a hot-melt of ionomer films (Surlyn 1702, Du-Pont) used as spacers between the electrodes. A drop of electrolyte solution was put on each of the drilled holes in the counter electrodes of the assembled cells.

2.4. DSSC performance

Photoresponse of the DSSC was evaluated by recording I-V characteristics with a 10 kΩ potentiometer as a variable load as shown in Fig .2.

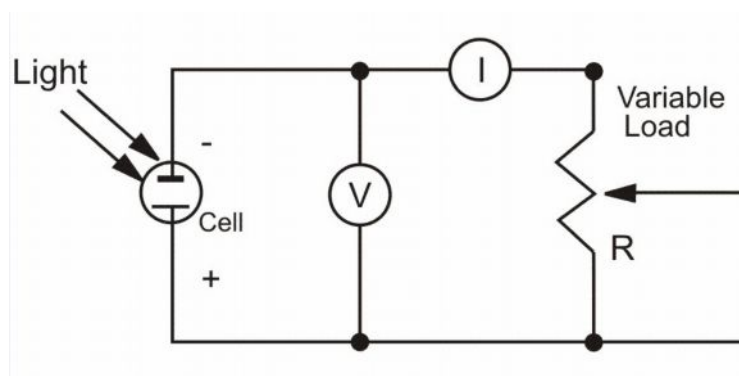


Fig.2 Experimental setup for measuring the current– voltage characteristics.

The I–V characteristics of the fabricated solar cells were measured under illumination (area of 1 cm²). For illumination, tungsten halogen lamp [OSRAM, Germany] was used with an incident light of 300 W/m².

3. Results

The sponge-like structure in SEM image of the top view of TiO₂ film coated on TCO electrode is shown in Fig. 3. The film is about 12 μm thick and the spherical TiO₂ nanoparticles are homogeneously distributed within the TiO₂ layer. No fracture on the surface and no gaps between the coatings were

observed, indicating excellent inter-particle connectivity and inter-layer attachment. Pomegranate juice mainly contains cyanin derivatives and exists as flavylum at natural pH.

Flavylum is red in color and strongly bonds with Ti⁴⁺ via emanating H₂O molecule [9]. The absorption spectra of nanocrystalline TiO₂ covered with freshly squeezed pomegranate juice is illustrated in Fig. 4. An intense absorption band in the visible region with a peak at 522 nm is observed caused by chelation of flavylum with TiO₂ [10].

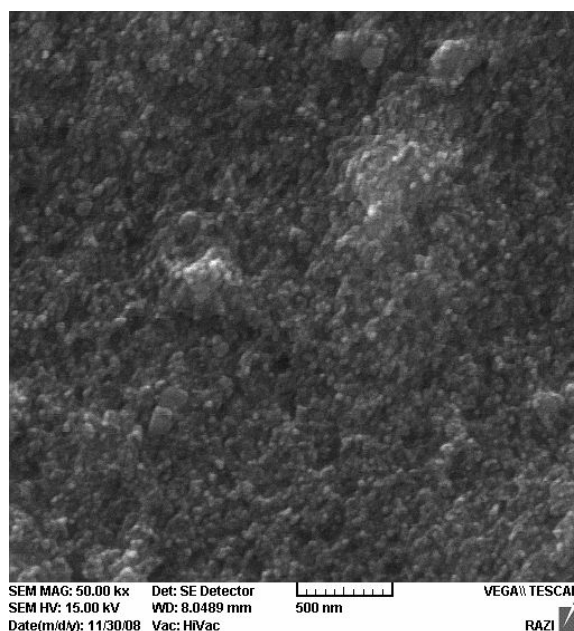


Fig.3 Top view of SEM micrographs of TiO₂ film coated on FTO glass.

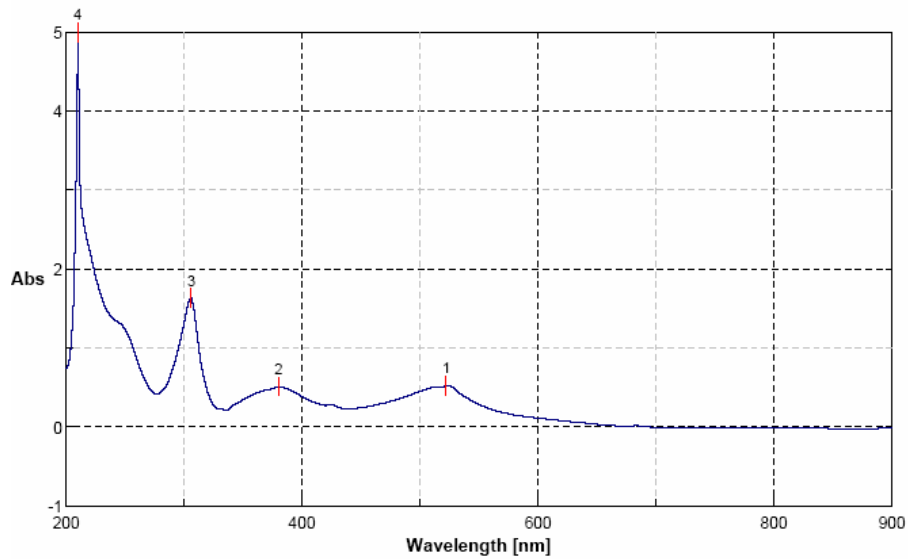


Fig.4 Spectral response of TiO₂ electrode coated with pomegranate juice.

The I-V curve for two fabricated cells is shown in Fig .5.

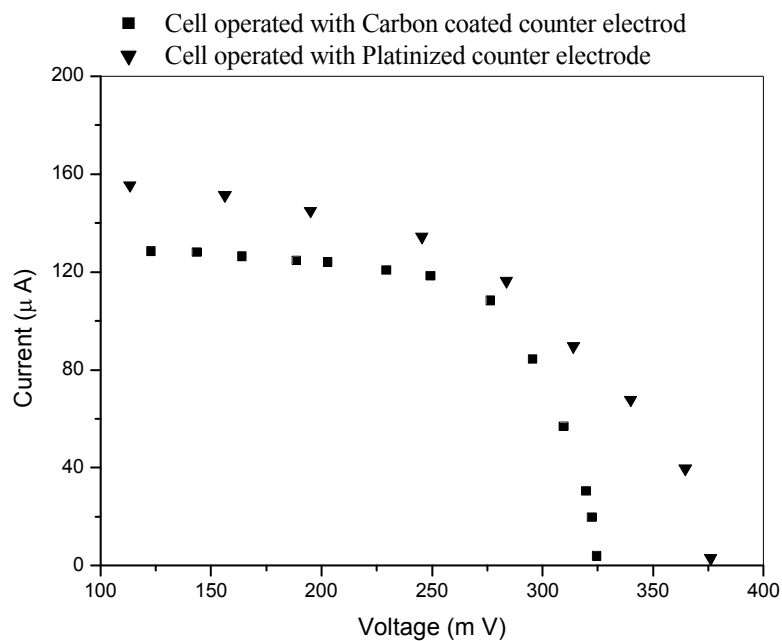


Fig.5 Photovoltaic response of fabricated DSSCs under illumination.

The values of V_{OC} , I_{SC} , FF and cell efficiency (η) for both cells of active area 1 cm^2 illuminated by a halogen lamp with an incident light of 300 W/m^2 are shown in table 1. As seen in table 1 the FF values for both cells are equal, indicating the types of counter

electrode used in this work have no effect on FF. The use of platinum deposited counter electrode facilitates the electron transfer process to regenerate the electrolyte in the cell explaining the higher I_{SC} and V_{OC} values over the carbon coated counter electrode.

Table1. Photovoltaic performance for fabricated cells.

DSCC	V _{oc}	I _{sc}	FF%	η
Operated with Carbon Coated Electrode	360	175	45	0.9
Operated with Platinum Coated Electrode	400	200	45	1.5

Conclusion

Natural pomegranate juice was used as sensitizer in dye-sensitized solar cell. Although the photovoltaic performance of fabricated DSSCs operated with Platinum coated over carbon coated counter electrode has shown an increase in I_{sc}, V_{oc} and cell conversion efficiency, it was shown that the type of counter electrodes used in this study has no effect on fill factor of fabricated natural DSSCs.

References

- [1] B. O'Regan and M. Grätzel, A low-cost, high-efficiency solar cell based on dye-sensitized colloidal TiO₂ films, *Nature* **353** (1991), pp. 737–740.
- [2] Tachibana, Y.; Moser, J. E.; Gratzel, M.; Klug, D. R.; Durrant, J. R. Subpicosecond Interfacial Charge Separation in Dye-Sensitized Nanocrystalline Titanium Dioxide Films. *J. Phys. Chem.* 1996, **100**, 20056-20062.
- [3] Hannappel, T.; Burfeindt, B.; Storck, W.; Willig, F. Measurement of Ultrafast Photoinduced Electron Transfer from Chemically Anchored Ru-Dye Molecules into Empty Electronic States in a Colloidal Anatase TiO₂ Film. *J. Phys. Chem. B* 1997, **101**, 6799-6802.
- [4] Moser, J. E.; Noukakis, D.; Bach, U.; Tachibana, Y.; Klug, D. R.; Durrant, J. R.; Humphry-Baker, R.; Grätzel, M. Comment on "Measurement of Ultrafast Photoinduced Electron Transfer". *J. Phys. Chem. B* 1998, **102**, 3649-3650.
- [5] Nazeeruddin, Md. K.; Pechy, P.; Gratzel, M. Efficient panchromatic sensitization of nanocrystalline TiO₂ films by a black dye based on a trithiocyanato-ruthenium complex. *Chem. Commun.* 1997, 1705-1706.
- [6] Kohle, O.; Ruile, S.; Gratzel, M. Ruthenium(II) Charge-Transfer Sensitizers Containing 4,4-Dicarboxy-2,2-bipyridine. Synthesis, Properties, and Bonding Mode of Coordinated Thio- and Selenocyanates. *Inorg. Chem.* 1996, **35**, 4779-4787.
- [7] Seok-Soon Kim, et al, Electrodeposited Pt for cost-efficient and flexible dye-sensitized solar cells. *Electrochimica Acta* **51** (2006) 3814–3819
- [8] S. Ito, M.K. Nazerudin, P. Liska, P. Comte, R. Charvet, P. Péchy, M. Jirousek, A. Kay, S.M. Zakeeruddin and M. Grätzel, Photovoltaic characterization of dye-sensitized solar cells: effect of device masking on conversion efficiency, *Prog. Photovolt.: Res. Appl.* **14** (2006), pp. 589–601
- [9] N.J. Cherepy, G.P. Semestad, M. Gratzel and J.Z. Zhang, *J. Phys. Chem. B* **101** (1997), pp. 9342–9351
- [10] Q. Dai and J. Rabani, *Chem. Commun.* (2001), pp. 2142–214
